

Mechanical instabilities of metals

Temperature changes during deformation are indices of fundamental processes

CARLO E. BOTTANI and GIUSEPPE CAGLIOTI, Istituto di Ingegneria Nucleare, CeSNEF, Politecnico di Milano

Abstract

In the general context of the non-linear thermodynamics of irreversible phenomena, the thermoelastoplastic transition occurring at the boundary between the thermoelastic and thermoplastic regimes of deformation of metallic materials can be seen as a bifurcation point. This non-equilibrium phase transformation is detected by measuring the temperature changes in a sample undergoing deformation, since these are indices of fundamental processes: initial cooling under adiabatic conditions due to the thermoelastic effect (Lord Kelvin, 1851) is suddenly followed by a rise in temperature caused by entropy production in the highly irreversible thermoplastic regime beyond the bifurcation. Thermal emission (TE) at and beyond yielding can also be usefully exploited, together with acoustic emission if required, in the investigation of thermodynamic transformations or mechanical instabilities during which mechanical work is converted into thermal energy, as in creep, fatigue and fracture, for example.

Riassunto

Instabilità meccaniche dei metalli. Le variazioni di temperatura durante la deformazione riflettono processi fondamentali a monte

La transizione termoelastoplastica al limite fra il regime di deformazione elastica e il regime di deformazione plastica dei materiali metallici, è interpretata come un punto di biforcazione nel quadro della termodinamica non lineare dei fenomeni irreversibili. Questa trasformazione di fase di non equilibrio può essere rilevata misurando le variazioni di temperatura del campione durante la deformazione: al raffreddamento iniziale durante una trazione adiabatica del metallo, dovuto all'effetto termoelastico (Lord Kelvin, 1851), segue un innalzamento della temperatura dovuto alla produzione di entropia nel corso della deformazione plastica, altamente irreversibile, al di là della biforcazione. Si può così rilevare e analizzare l'emissione termica (ET) che si produce nell'intorno e al di là dello snervamento. Altre possibili applicazioni dell'ET (eventualmente in parallelo all'emissione acustica) si profilano nella ricerca su trasformazioni termodinamiche o instabilità meccaniche nel corso delle quali il lavoro meccanico sia convertito in energia termica, ad esempio durante lo scorrimento viscoso, la fatica e la frattura.

Traditionally, studies of the mechanical behaviour of solids are the prerogative of mechanical engineers or applied mathematicians. The former are generally more interested in deriving descriptions of the performance of structures rather than in understanding more basic aspects of the behaviour of condensed matter. Their analyses are usually based on the implicit assumption that mechanical transformations are indeed purely mechanical. Temperature is a parameter which enters as a static operating condition or, in certain instances, as determining the rates of processes that are thermally activated. Its role as a response to mechanically induced dynamic changes of state is generally ignored.

Applied mathematicians, on the other hand, tend to base their calculations on idealized models where discontinuities are introduced *a priori*, so that, for instance, a yielding surface in the stress tensor space is postulated rather than discovered as an inevitable result of a more fundamental model of material behaviour.

It is for the physicist to fill the gap between the basic micromechanisms taking place in the structure of real materials which contain defects and the dynamical processes of self-organisation occurring in materials which are driven off equilibrium. These processes are responsible for the strength of engineering structures. In such a task, the detailed function of temperature as a dynamic component cannot be ignored.

In order to define the state of a thermodynamic system in local equilibrium, or slightly removed from global equilibrium, the local temperature, i.e. the state variable conjugated to the local entropy in the local Helmholtz thermodynamic potential, is hierarchically as necessary

as the strain tensor which is the set of state variables conjugated to the stress tensor.

Temperature and deformation turn out to be non-linearly coupled, and any local deformation transient produces a local temperature change. This coupling is in evidence even before the onset of plasticity, indeed, throughout the Hookean regime of elasticity.

Thermoelastic effect

We begin with the simplest "mechanical" transformation immediately preceding the onset of plasticity which is essentially a thermoelastic deformation.

When a metallic sample is stretched by ϵ_z during a non isothermal tensile test, its relative cross-sectional area shrinks by $2\nu\epsilon_z$ (ν being the Poisson ratio) and the relative volume of the sample increases by

$$\Delta V/V = (1-2\nu)\epsilon_z$$

If the time needed to produce this volume increase is both

- short with respect to the heat diffusion time along the sample axis and
- long enough to make the heat production by viscous effects negligible, the approximation of an isentropic process ($\Delta S = 0$) should apply.

The components of ΔS to be considered are:

- 1) the usual thermal entropy change, $C_v \Delta T/T_0$, where C_v is the specific heat at constant volume and T_0 is the operating temperature;
- 2) the configurational entropy change associated with the deformation, i.e. $(\partial S/\partial V)_T \times (1-2\nu)\epsilon_z V$. Using

Maxwell's relation $(\partial S/\partial V)_T = (\partial p/\partial T)_V$, where p is the pressure, and $(\partial p/\partial T)_V = -(\partial p/\partial V) \times (\partial V/\partial T)$, one obtains $(\partial S/\partial V)_T \times \beta/K_T$ in terms of the volume coefficient of thermal expansion, β , and the isothermal compressibility, K_T .

Isentropic conditions therefore lead to

$$\Delta T/T_0 = -\gamma(1-2\nu)\epsilon_z$$

where γ is the Grüneisen parameter $= \beta V/K_T C_V$. During a tensile test performed under these conditions, the sample cools down while undergoing deformation in the elastic region. The amount of temperature drop is proportional to the deformation (which is presumed to occur homogeneously within the bulk of the sample) and depends on the Grüneisen parameter, which reflects the anharmonicity of the interatomic forces and gives a measure of the thermomechanical coupling. At ordinary temperatures, γ lies between 1.5 and 2.5 for a wide range of metals.

The decrease in temperature we have noted is opposed by heating effects that stem from the viscosity of the metal. As the applied stress increases,

the initially sessile dislocations become more and more mobile and their motion within the sample generates an increasing amount of thermal energy. Consequently, in competition with the anharmonicity that gives rise to a stable thermoelastic cooling whose extent is determined by γ , a destabilizing mechanism with positive feedback is introduced through the incipient processes of plasticity. When the critical point is reached, the two mechanisms balance each other marking the boundary between the thermoelastic and thermoplastic regimes of deformation.

Thermoelastic limit stress

From a numerical standpoint, a metallic sample deformed at room temperature in practice cools down by no more than 1 K and so, in the past when temperature measurements, being based on thermocouples, were cumbersome, and the flow of heat from the clamps holding the sample could mask the effect, the change could be regarded as academic. The position has changed dramatically with the

Fig. 1 - A) Temperature, B) Stress, C) Strain vs time for a Standard slab of SAFC-40R steel previously deformed up to a total elongation of 1.4%
Note the initial thermoelastic cooling, followed by plastic heating.


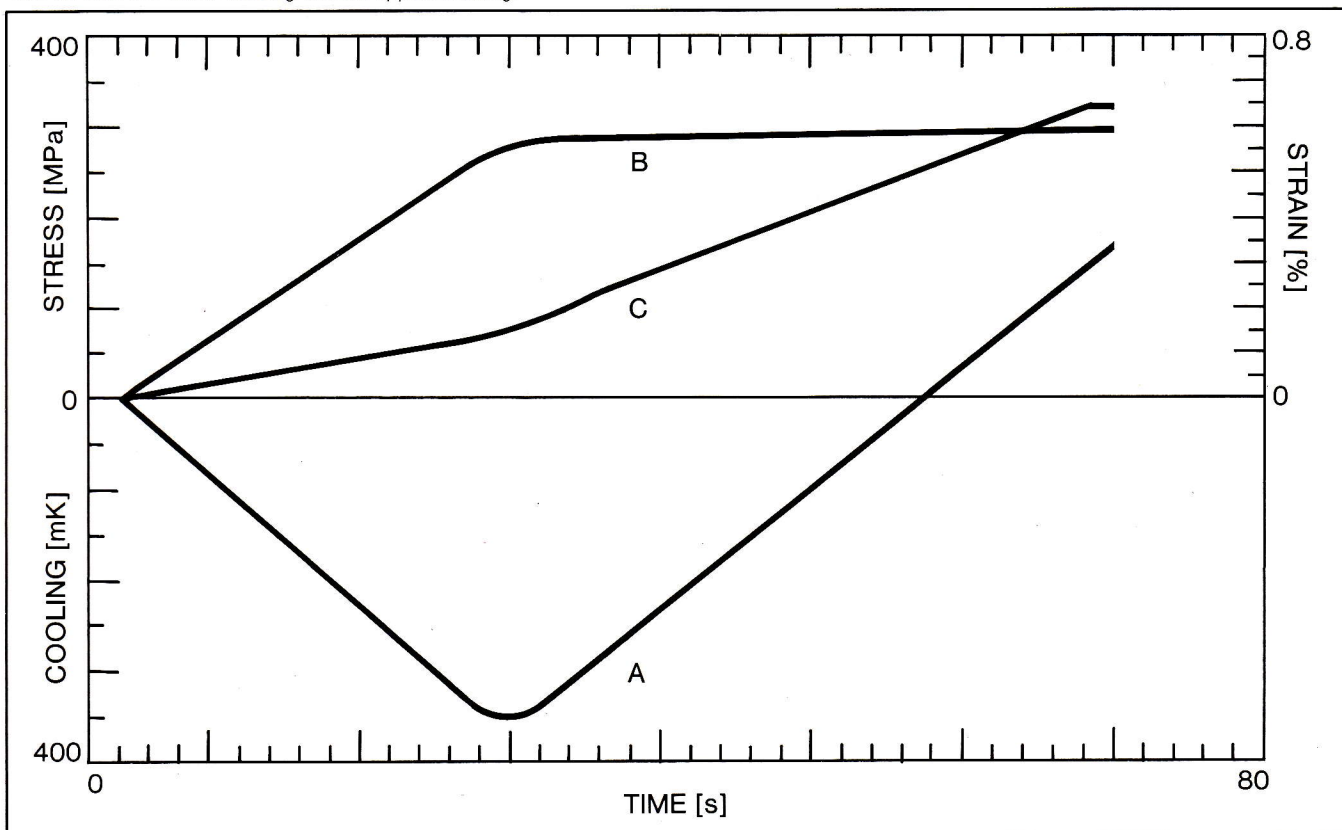


Fig. 2a - By eliminating time between curves A) and B) of Fig. 1, one obtains the T vs σ characteristic. This shows a sudden change in the temperature trend at a thermoelastoplastic limit stress of 264 MPa.

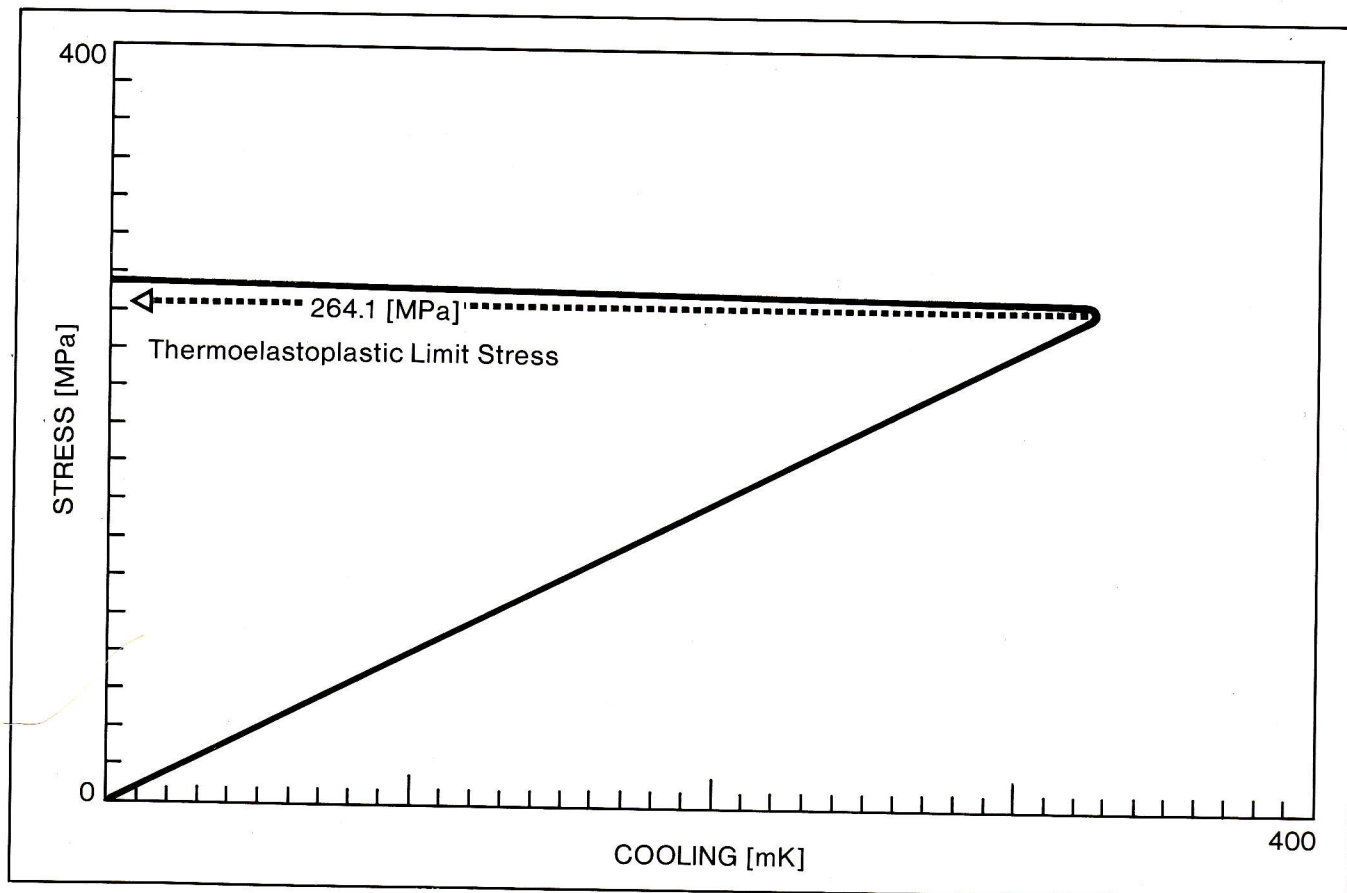

introduction of prompt semiconductor thermistors and it is now possible to measure reproducible changes of 0.001 K and less. This has permitted the production of characteristic stress curves such as that shown in Fig. 1.


The stress corresponding to the critical point marking the boundary between the Hooke-Kelvin thermoelastic and the thermoplastic regimes, we refer to as the thermoelastoplastic limit stress σ_θ or, simply, the thermoelastic limit (Fig. 2a). The value of σ_θ turns out to be slightly smaller than the yield strength $\sigma_{0.2}$ currently derived from the stress-strain characteristic following standard procedures (Fig. 2b). However, its unambiguous definition could, we believe, eliminate the empirical safety (or ignorance) factors, commonly attached to $\sigma_{0.2}$ in structural design, even if only gradually. The temperature rise occurring at stress values immediately above σ_θ clearly marks the onset of the irreversible and irrecoverable behaviour of materials. Its adoption would allow the actual "yield" point of a material to be pinpointed with greater precision than can be obtained from $\sigma_{0.2}$.

Theoretical treatment

Within the frame of the non-linear thermodynamics of irreversible phenomena, σ_θ could be interpreted as a bifurcation point: there, the linear thermodynamic branch becomes unstable while, under the control of the imposed deformation, a large temperature fluctuation grows as a component of the order parameter which "enslaves" the system and promotes its dynamical reorganization.

A model has been developed to explore the main features of this instability that is formally based on a system of two non-linear partial differential equations in the unknown temperature and deformation fields, expressing the balance of entropy and linear momentum within a sample undergoing a tensile test. The linearized equations associated with the above system determine the fluctuations of temperature and deformation around the time-dependent reference state, represented by the thermoelastic branch. The fluctuations are expanded in normal modes and the amplitudes of these temperature and deformation

Fig. 2b - By eliminating time between curves B) and C) of Fig. 1, one obtains the σ vs ϵ characteristic. By the standard 0.2% off-set method, a conventional yield strength value of 273 MPa is obtained. Due to work hardening, the two characteristic stresses differ by only about 10 MPa. In general, for an annealed steel sample exhibiting a smooth elastoplastic transition these two stresses differ by a few tens of MPa.

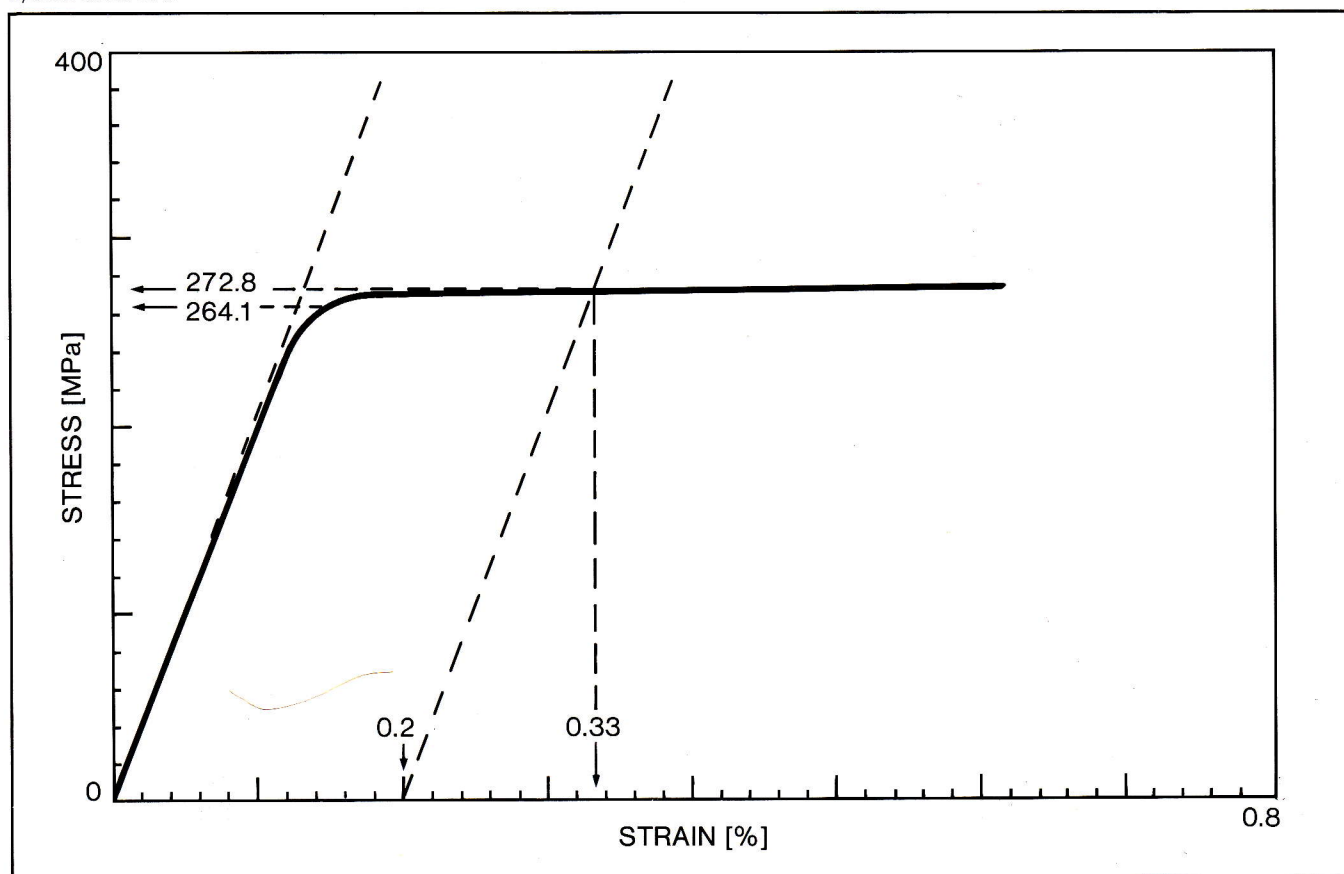

modes obey a system of linear equations. A linear stability analysis gives the threshold value of the control parameter at which the amplitude of the least damped, i.e. the fundamental mode, eventually diverges. The above model refers to an ideally homogeneous anharmonic solid, where the defect contribution to the local thermodynamic functions is lumped in an effective phenomenological Grüneisen parameter. As such, the picture below for thermal emission based on the development of this model should be given only a qualitative value.

Thermal emission

The amplitude of the fundamental mode provides a measure of the fluctuations of both the temperature and the deformation. In our case, this mode is thermoacoustic with a frequency that is a complex number, the imaginary component of which equals that of the fundamental sound wave of the structure. In a thermoelastic anharmonic solid, thermal energy

fluctuations and, consequently, temperature can also propagate in a wave-like fashion. The real component of the frequency represents the damping, and depends strongly on the size of the control parameter, i.e. the applied deformation. It is negative in the elastic region, but becomes positive across the thermoelastic critical point. Correspondingly, the order parameter exhibits a continuous transition from a zero mean value to a finite size: the originally incoherent phonon field tends to become partially coherent, as in the initial stage of the single mode continuous laser dynamic instability. In our opinion, this is the origin of acoustic emission and, at the same time, of what one might call *thermal emission*.

Thermal emission during yielding has been detected and analyzed so far in hundreds of samples of metallic structural materials of which Figs. 1 and 2 represent only one instance. Here the knowledge of yield in the sample "as received" and after deep drawing into the shape of a car body is important in order to ascertain the mechanical performance of the recently developed high strength low alloy (HSLA) steels.

Plastic regime

In the plastic regime a fraction of the mechanical work done to deform plastically a solid body is unavoidably converted into heat through e.g. internal friction and the extensive irreversible motion of defects. At room temperature this fraction can reach about ninety per cent. Dissipation of this heat gives rise to a considerable increase in temperature which, in turn, modifies the mechanical susceptibility of the material itself (softening). Although at lower temperatures, because the metal is a poorer heat conductor, the fraction is more modest, a positive feedback can still originate in the deformation band via thermally activated processes of dislocation motion. In turn, plastic flow can exhibit higher order instabilities (e.g. the oscillatory behaviour of serrated yielding).

The physical index of dissipation is the entropy production (the specific entropy produced per unit time). In purely reactive diffusive systems as are to be found in chemical systems, this quantity controls the stability, whereas in a solid undergoing large deformations, while temperature stands as a relevant physical variable, the entropy production alone is no longer sufficient to provide a criterion for stability. Detailed models of cooperative defect kinetics must be worked out in addition.

Consequently, it seems advisable to extend the treatment proposed for the thermoelastic instability to other dynamic instabilities exhibited by materials under stress. We allude to creep, fatigue and fracture. Finally, it is suggested that real-time monitoring of the temperature of metallic materials undergoing deformation might provide a means of detecting and highlighting internal mechanical processes responsible for the instabilities.

Acknowledgement

The data in Figures 1 and 2 were obtained, with a patented instrumentation under a contract between Alfa Romeo and the Politecnico di Milano.

REFERENCES

- Boffi, S., C.E. Bottani, G. Caglioti, and P.M. Ossi. Strain driven thermoelastic instability toward brittle fracture. *Zeit. Phys. B.*, **39** (1980), 135.
- Bottani, C.E. Thermoacoustic instabilities in strained solids: a synergetic approach. In G. Caglioti and A. Ferro Milone (Eds.), *Proceed. of the Varenna International School of Physics "E. Fermi". Mechanical and thermal behaviour of metallic materials*, North Holland Publ., Amsterdam, 1982, pp. 278-414.
- Bottani, C.E. and G. Caglioti. Thermal emission: a probe to identify the critical point of the elastoplastic transition, *Materials Letters*, **1** (1982), 119-121.
- Bottani, C.E., and G. Caglioti. Thermoelastic instabilities in metals. In *Proceed. of the EPS Condensed General Conference*, Manchester, March 22-25, 1982, *Phys. Scripta*, **TI**, pp. 65-70.
- Bottani, C.E., G. Caglioti, A. Novelli, P.M. Ossi, F. Rossitto, and G. Silva. Il limite elastoplastico: realtà fisica e attuali criteri di qualificazione. *Metallurgia Italiana*, **74** (1982), 530.
- Bottani, C.E., G. Caglioti, and P.M. Ossi. Grüneisen parameter: measurement of the strain derivatives. *J. Phys. F*, **11** (1981), 541.
- Caglioti, G. The thermoelastic effect: statistical mechanics and thermodynamics of the elastic deformation. In *Proceed. of the Varenna School of Physics "E. Fermi"*, cit., pp. 1-34.
- Charles, J.A., J.E. Francis, and F.J. Appl. Fatigue damage determination using thermograph. In *Proceed. of the Second Intern. Conference on Mechanical behaviour of materials*. ICM II, Boston, August 16-20, 1976, pp. 817-821.
- Gilman, J.J. A unified view of flow mechanisms in materials. In A.S. Argon (Ed.), *Physics of strength and plasticity*. MIT Press, Cambridge, 1969, pp. 3-13.
- Haken, H. *Synergetics*. An introduction. 2nd enlarged edition, Springer, Berlin, 1978.
- Huang Yih and Shyr Jun. Application of infrared technique to research on tensile test. In the *Institute of Metal Research of the Academia Sinica* (private communication), 1980.
- Nabarro, F.R.N. *Theory of crystal dislocations*. Clarendon Press, Oxford, 1967, pp. 703.
- Nicolis, G., and I. Prigogine. *Self-organization in nonequilibrium systems*. Wiley and Sons, New York, 1977.
- Venkataraman, G. Fluctuations and mechanical relaxation. In *Proceed. of the Varenna Intern. School of Physics "E. Fermi"*, cit., pp. 278-414.